



Scintillation and luminescence properties of a single CsCaCl₃ crystal



M. Koshimizu^{a,*}, N. Yahaba^a, R. Haruki^b, F. Nishikido^c, S. Kishimoto^d, K. Asai^a

^a Department of Applied Chemistry, Graduate School of Engineering, Tohoku University, 6-6-07 Aoba, Aramaki, Aoba-ku, Sendai 980-8579, Japan

^b Advanced Science Research Center, Japan Atomic Energy Agency, 2-4 Shirakata Shirane, Tokai, Ibaraki 319-1195, Japan

^c Molecular Imaging Center, National Institute of Radiological Sciences, Anagawa 4-9-1, Inage-ku, Chiba 263-8555, Japan

^d Institute of Materials Structure Science, High Energy Accelerator Research Organization, 1-1 Oho, Tsukuba, Ibaraki 305-0801, Japan

ARTICLE INFO

Article history:

Available online 22 April 2014

Keywords:

Auger-free luminescence
Core-valence luminescence
Core hole
Scintillator
Self-trapped exciton

ABSTRACT

We synthesized a fast scintillation material based on a ternary halide crystal, CsCaCl₃, which is known to exhibit Auger-free luminescence (AFL) under core-level excitation. We characterized its luminescence properties using vacuum ultraviolet (VUV) light for excitation. We observed a broad AFL band centered at approximately 300 nm for the core hole excitation, with a decay time of 2.3 ns. In addition to AFL, we observed several luminescence bands for interband and sub-band-gap excitation. The scintillation light yield was estimated to be 410 photons/MeV. We observed a fast scintillation component due to the AFL having a decay time constant of 2.3 ns. This fast component accounts for 58% of the total scintillation. These results indicate that a fast scintillation material was successfully fabricated, employing AFL as the luminescence mechanism based on a ternary halide crystal.

© 2014 Elsevier B.V. All rights reserved.

1. Introduction

Auger-free luminescence (AFL), or core-valence luminescence, is a radiative electronic transition between the valence band and the outermost core band [1]. This luminescence is observed only for insulator crystals in which the band-gap energy is larger than the energy difference between the valence band and the outermost core band. AFL is known to be a fast luminescence process whose decay time constant is typically of the order of nanoseconds or less. Therefore, insulator materials that exhibit AFL are applicable as to fast-response scintillators.

Thus far, BaF₂ has been the most successful example of scintillators exhibiting AFL. Its scintillation has a fast component corresponding to AFL, whose decay time constant is as short as 0.8 ns [2]. Owing to this fast decay combined with relatively high light yields, BaF₂ has been used for applications in which good timing characteristics are necessary. However, its scintillation also has a long decay component corresponding to self-trapped excitons (STEs). The decay time constant of the long component has been reported to be 600 ns [2]. Thus, the long component limits the usage of BaF₂ in several applications, such as measurements with a high counting rate. AFL has also been observed in other binary halide crystals [3], such as RbF, CsF, CsCl, and CsBr. In those materials, the light output of AFL is lower than BaF₂, and they similarly

have long components corresponding to STEs. Because the number of binary halides exhibiting AFL is limited, research should be extended to ternary or more complex halide crystals in order to develop novel scintillation materials exhibiting AFL.

Recently, AFL has been observed with several ternary halide crystals, such as LiBaF₃ [4], MgBaF₄ [4], CsCaCl₃ [4,5], Cs₂ZnCl₄ [6,7], Rb₂ZnCl₄ [8]. Among these, we have focused on the CsCl-based ternary crystals, because AFL occurs in the long wavelength region and so is suitable for detection with photomultiplier tubes (PMTs). In a study reported recently, we found a fast scintillation component due to AFL in Cs₂ZnCl₄ [9]. In this paper, we report the scintillation properties of another halide crystal, CsCaCl₃.

2. Experiment

Single crystals of CsCaCl₃ were fabricated using a vertical Bridgman-Stockbarger method. Powders of CsCl (99.999%, Kojundo Chemical Laboratory Co. Ltd., Japan) and CaCl₂ (99.99%, Sigma-Aldrich, Japan) were mixed in a stoichiometric ratio. The mixed powder was poured into a quartz ampoule and heated at 473 K in vacuum for 1 day in order to remove water. During the growth, the temperature gradient was 1.1 K/mm, and the ampoules were lowered at a rate of 1.0 mm/h. Transparent crystals were obtained. The photo of the sample crystal is shown in Fig. 1. The size was approximately 3 × 5 × 2 mm². They showed a slight hygroscopy. When we left the crystals in air for several days, the surface of the crystals turned cloudy.

* Corresponding author. Tel.: +81 22 795 7219.

E-mail address: koshi@qpc.che.tohoku.ac.jp (M. Koshimizu).

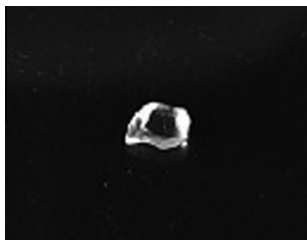


Fig. 1. Photograph of the sample crystal.

The luminescence properties were characterized using vacuum ultraviolet (VUV) light as an excitation source. The measurements were performed at beamline 7B of the UVSOR facility at the Institute for Molecular Science, Japan. The synchrotron radiation was monochromated using a 3-m normal-incidence monochromator. The samples were irradiated with the monochromated light in a vacuum chamber. The luminescence spectra were measured using a charge coupled device (CCD) equipped with a monochromator. The luminescence was guided to the detector via an optical fiber. The luminescence spectra were measured for various excitation wavelengths, and the excitation spectra were obtained from the luminescence spectra. In addition, luminescence decay behavior was observed by a single photon counting method. The single-bunch operation mode was used, and the period between successive pulses was 176 ns. The decay component longer than this period appeared as a time-independent component in the time profiles. The luminescence photons were detected with a multi-channel-plate (MCP) mounted PMT (R3809U-50, Hamamatsu, Japan). All measurements were performed at room temperature.

The scintillation properties and X-ray detection capability were characterized at BL-14A at the Photon Factory, KEK, Japan. The X-ray energy was 67.4 keV. For the characterization of the X-ray detection capability, the sample crystals were attached to a PMT (R7400P, Hamamatsu, Japan) with a small amount of optical grease. The pulse-height spectra were measured using a charge sensitive preamplifier (2005, Canberra, CT, US), a main amplifier (572A, Ortec, TN, US), and a multichannel analyzer (MCA; 5004, Apte, NY, US). The single bunch operation mode was used for the measurements of scintillation time profiles. The period between each successive pulse was 624 ns. The spacing between the samples and the PMT was ~ 38 mm. The single-photon detection signals from the PMT were amplified with a fast preamplifier (6954, Phillips Scientific, NJ, US). The timing of the amplified signals was determined with a constant-fraction discriminator (CFD; 935, Ortec, TN, US), and the timing signals were fed to a time-to-amplitude converter (TAC; 566, Ortec, TN, US) as start signals. The X-ray arrival timing signals were supplied from the synchrotron facility and fed to the TAC as stop signals. The time difference between the two signals was compiled into a histogram with the MCA, and yielding the time profiles.

3. Results and discussion

3.1. VUV spectroscopy

Fig. 2 shows the luminescence spectra of CsCaCl₃ excited at 170–200 nm. Considering the band-gap energy of 8.5–8.6 eV reported previously [5,10], these excitation wavelengths correspond to the sub-band-gap excitation. Thus, the observed luminescence originates from electronic transitions in the band gap, and we attribute this to impurities or defects. Because we did not use an optical filter to remove the scattered excitation photons, the second-order and third-order diffraction peaks appeared as sharp

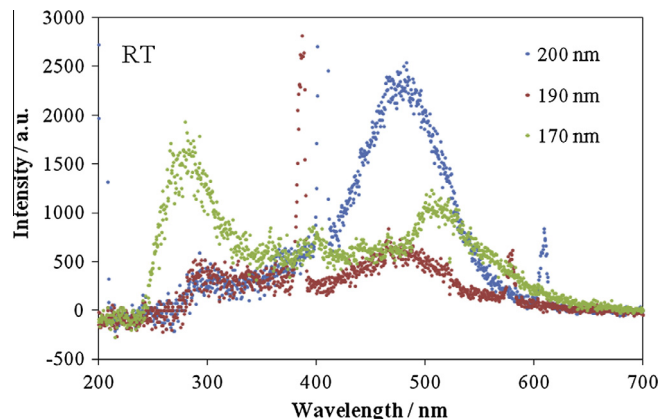


Fig. 2. Luminescence spectra of CsCaCl₃ for the excitation at 170–200 nm.

peaks. For excitation at 200 nm, we observed a broad band at 480 nm and a shoulder at approximately 290 nm. For shorter excitation wavelengths down to 170 nm, the intensity of the two bands reversed. In addition, we observed a band at 510 nm for excitation at 170 nm. The results indicate that the CsCaCl₃ crystal had at least two kinds of defect or impurity sites involved in the luminescence. One plausible origin is anion vacancies, which is common lattice defect in halide crystals. Another possible origin is cation vacancies due to a slight deviation of the cation composition from stoichiometry.

Fig. 3 shows the luminescence spectra of CsCaCl₃ excited at 160 and 130 nm. We observed a broad band peaking at approximately 440 nm for both excitation wavelengths or between them. The photoexcitation at 130 nm corresponds to the interband excitation. The photon energy at 160 nm is slightly lower than the band-gap energy, and may correspond to an exciton excitation [5]. Thus, this broad band is ascribed, presumably, to STEs.

Fig. 4 shows the luminescence spectra for excitation at 84–88 nm. Considering the position of the outermost core level of Cs, 14 eV below the conduction band [5,10], these excitation wavelengths correspond to core-level excitation. The spectrum for excitation at 84 nm differs considerably from those for the excitation wavelengths of 88 and 86 nm. For the excitation wavelength of 88 nm, the luminescence spectrum was quite similar to those for the excitation wavelengths of 130 or 160 nm shown in Fig. 3. For the excitation wavelength of 86 nm, in addition to the band centered at 440 nm, a small shoulder was observed at ca. 300 nm. For the excitation wavelength of 84 nm, a prominent broad band was observed at 300 nm, and a clear band was also observed at 500 nm. The spectrum for the excitation at 84 nm is quite similar to that in previous reports [5,10], and a broad band centered at

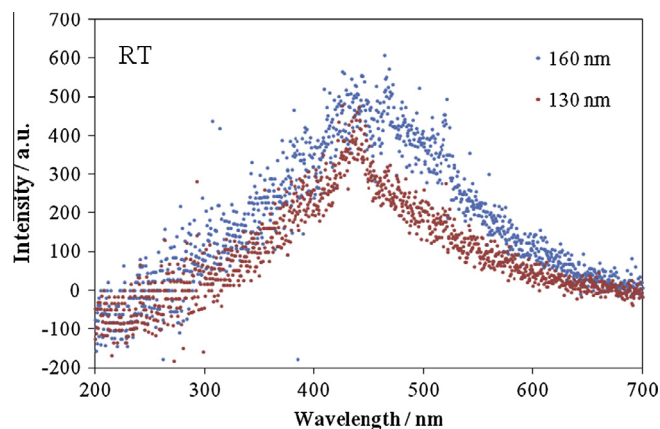


Fig. 3. Luminescence spectra of CsCaCl₃ for the excitation at 160 and 130 nm.

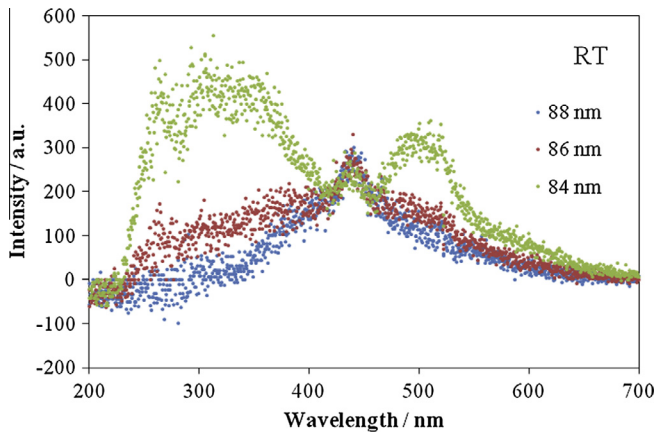


Fig. 4. Luminescence spectra of CsCaCl₃ for excitation at 84–88 nm.

300 nm can be ascribed to AFL. A peak at approximately 500 nm may be due to second-order diffraction of the 300 nm band.

Fig. 5 shows the excitation spectra for the 300 nm luminescence band. In order to analyze the entire range of the broad band at 300 nm, the luminescence wavelengths were set at 260, 310, and 350 nm. These wavelength correspond to the short-wavelength edge, center, and the long-wavelength edge of the broad band, respectively. A steep rise at approximately 84 nm was observed over the entire range of the broad luminescence band at 300 nm. These excitation spectra were quite similar to those in previous reports [5,10], and the result clearly indicates that the broad band at 300 nm is due to AFL.

Fig. 6 shows the luminescence time profiles for excitation at 84 and 200 nm. For the excitation at 84 nm, we observed fast luminescence decay in the entire range of the broad band at 300 nm, and Fig. 6(a) illustrates the time profiles at short- and long-wavelength regions of the band. The decay time constant was estimated to be 2.3 ns, which is consistent with the result reported in a previous paper [5]. In contrast, for the excitation at 200 nm, the time profiles were flat. Because the period between the successive excitation pulses was 176 ns, this result indicates that the decay time constant of the luminescence is longer than several hundreds of nanoseconds.

3.2. Characterization of scintillation properties

Fig. 7 shows the pulse-height spectrum of a scintillation detector equipped with the CsCaCl₃ crystal for the X-ray energy of 67.4 keV. The pulse height spectrum for YAlO₃:Ce (YAP:Ce) is also shown for comparison. It should be noted that the amplifier gain

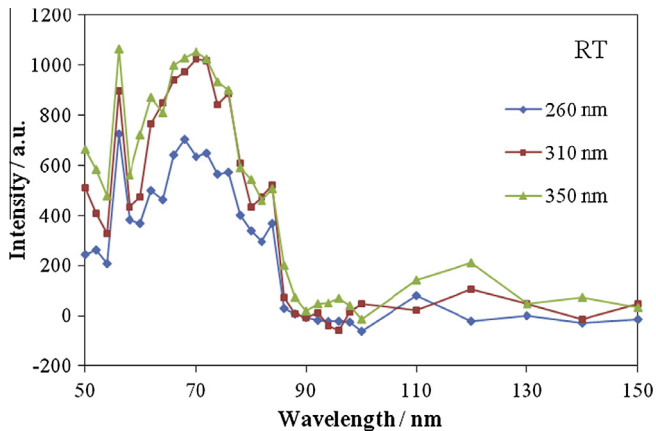


Fig. 5. Excitation spectra of CsCaCl₃.

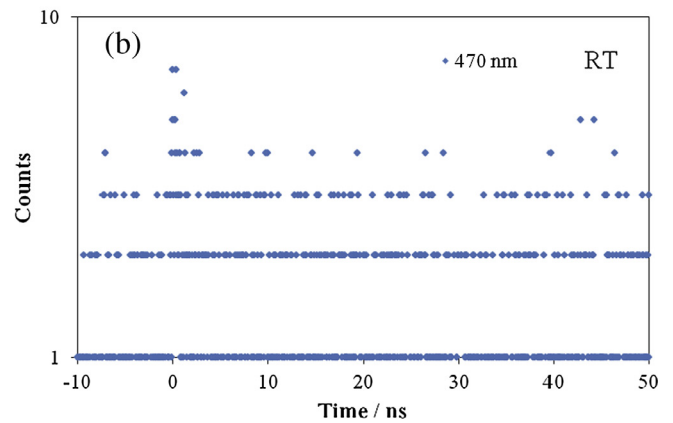
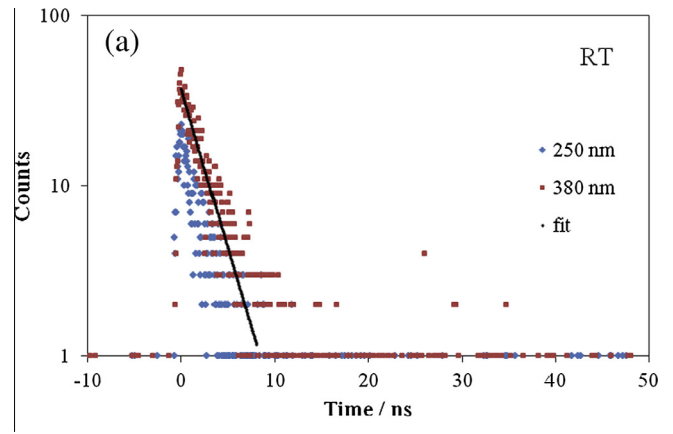


Fig. 6. Luminescence time profiles of CsCaCl₃ for excitation at (a) 84 nm and (b) 200 nm.

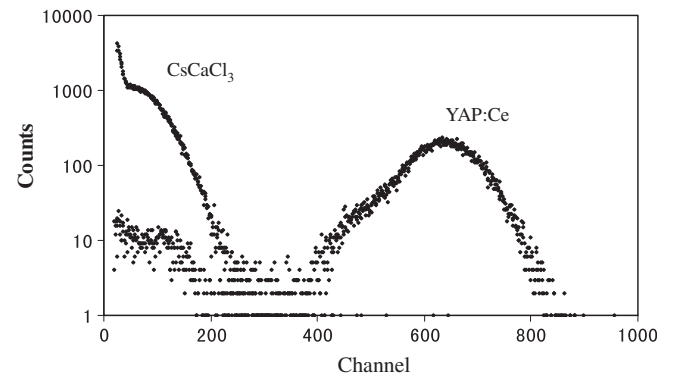


Fig. 7. Pulse-height spectra of scintillation detectors equipped with a CsCaCl₃ or a YAlO₃:Ce (YAP:Ce) crystal for 67.4 keV X-ray. Note that the amplifier gain was ten times smaller for YAP:Ce.

was ten times smaller for YAP:Ce. A broad shoulder was observed at approximately 100 ch for CsCaCl₃. Assuming the light yield of YAP:Ce to be 18,000 photons/MeV [11], and considering the wavelength dependent sensitivity of the PMT, the light yield of the CsCaCl₃ crystal is estimated to be 410 photons/MeV.

Fig. 8 shows the scintillation time profile of CsCaCl₃. The decay behavior was satisfactorily fitted with a sum of two exponential-decay components and a time-independent component. The fast component had a decay time constant of 2.3 ns, which is consistent with that of the luminescence shown in Fig. 6. Thus, a fast scintillation component due to AFL was successfully obtained. The fast component accounts for 58% of the total scintillation. The slow component had a decay time constant of 14 ns, and this

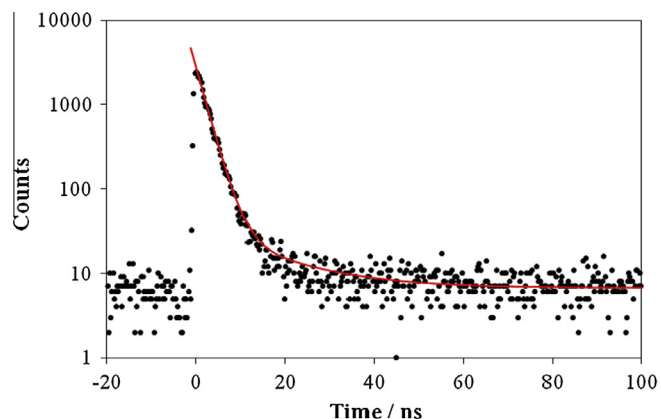


Fig. 8. Scintillation time profile of CsCaCl_3 . The solid line represents the fitted function.

component accounts for only 4% of the scintillation. The time-independent component accounts for 38%, and this component is considered to have a decay time constant much longer than 624 ns, which is the period of the successive X-ray pulses. The components having a long decay time constant are presumably ascribed to the luminescence at defects or impurities and STE emission, which were observed for the VUV excitation in Figs. 2 and 3.

4. Conclusion

We synthesized a fast scintillation material from a ternary halide crystal exhibiting AFL, CsCaCl_3 . For the VUV excitation, we

observed a broad band centered at 300 nm having a decay time constant of 2.3 ns and ascribed this band to AFL. For interband excitation and sub-band-gap excitation, we observed several bands due to radiative decay of STEs and luminescence at defects or impurities, respectively. The scintillation light yield was estimated to be 410 photons/MeV. We observed a fast scintillation component having a decay time constant of 2.3 ns and ascribed this component to AFL. This fast component accounts for 58% of the total scintillation. These results indicate that a fast scintillation material was successfully fabricated from a ternary halide crystal by using AFL.

References

- [1] P.A. Rodnyi, *Radiat. Meas.* 38 (2004) 343.
- [2] M. Laval, M. Moszynski, R. Allemand, E. Cormoreche, P. Guinet, R. Odru, J. Vacher, *Nucl. Instrum. Methods* 206 (1983) 169.
- [3] P.A. Rodnyi, M.A. Terekhin, *Phys. Status Solidi B* 166 (1991) 283.
- [4] J. Jansons, Z. Rachko, J. Valbis, J. Andriessen, P. Dorenbos, C.W.E. van Eijk, N.M. Khaidukov, *J. Phys.: Condens. Matter* 5 (1993) 1589.
- [5] I.A. Kamenskikh, M.A. MacDonald, V.V. Mikhailin, I.H. Munro, M.A. Terekhin, *Rev. Sci. Instrum.* 63 (1992) 1447.
- [6] A. Ohnishi, M. Kitaura, T. Otomo, M. Sasaki, *J. Phys. Soc. Jpn.* 72 (2003) 2400.
- [7] A. Ohnishi, M. Kitaura, M. Itoh, M. Sasaki, *J. Phys. Soc. Jpn.* 81 (2012) 114704.
- [8] A. Ohnishi, M. Saito, M. Kitaura, M. Itoh, M. Sasaki, *J. Lumin.* 132 (2012) 2639.
- [9] N. Yahaba, M. Koshimizu, Y. Sun, T. Yanagida, Y. Fujimoto, R. Haruki, F. Nishikido, S. Kishimoto, Keisuke Asai, *Appl. Phys. Express* (submitted for publication).
- [10] Ya. Chornodolskyy, G. Stryganyuk, S. Syrotyuk, A. Voloshinovskii, P. Rodnyi, *J. Phys.: Condens. Matter* 19 (2007) 476211.
- [11] M. Moszynski, M. Kapusta, D. Wolski, W. Klamra, B. Cederwall, *Nucl. Instrum. Methods Phys. Res., A* 404 (1998) 157.